

No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 1 of 19

CUSTOMER NAME: XIAMEN HUILIYUAN IMP.&EXP.CO.,LTD

ADDRESS: 204, NO.23-2, WANGHAI ROAD, SIMING DISTRICT, XIAMEN, FUJIAN

The following sample(s) was/ were submitted and identified on behalf of the client as:

Sample Name : OIL DRUM

SGS Ref. No. : GZIN1502006572MR-01

Product Specification : 20L

Date of Receipt : Feb 12, 2015

Date of second Receipt : Jun 17, 2015

Testing Start Date : Feb 12, 2015

Testing End Date : Jun 17, 2015

Test result(s) : For further details, please refer to the following page(s)

Signed for SGS-CSTC Standards Technical Services Co. , Ltd Xiamen Branch

Testing Center

Joy Zhang

Authorized signatory

Note: Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.





No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 2 of 19

Summary of Results:

No.	Test Item	Test Method	Result	Conclusion
1	Design	AS/NZS 2906:2001 Section 6	See results	See results
2	Elastomeric Components	AS/NZS 2906:2001 Section 7.2 & Appendix B & ASTM D471- 12a	See results	Pass
3	Mass Loss Test	AS/NZS 2906:2001 Section 7.3.1 & Appendix C	See results	Pass
4	Hydrostatic Pressure Test & Stability Test	AS/NZS 2906:2001 Section 7.3.2 , Section 7.3.3 & Appendix L	See results	Pass
5	Integrity Under Exposure to Flame Ttest	AS/NZS 2906:2001 Section 7.3.5 & Appendix F	See result	Pass
6	Drop Strength Test	AS/NZS 2906:2001 Section 7.3.4 & Appendix E	See results	Pass
7	Handle Strength Test	AS/NZS 2906:2001 Section 7.3.6 & Appendix G	No separation of the handle, no leakage	Pass
8	Resistance to Petroleum Test	AS/NZS 2906:2001 Section 7.4.2 & Appendix I & ASTM D638-10	See results	Pass
9	Stress Cracking Test	AS/NZS 2906:2001 Section 7.4.3 & Appendix J	See results	Pass
10	Marking*	AS/NZS 2906:2001 Section 8	See results	See results

Note: * means the test samples used are received in the second time.



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/ferms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic to the company state of the co

No.31 Xianghong Road, Xiang/kn Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765880 www.sgsgroup.com.cn 中国 ·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5761588 f (86-592) 5765380 e sgs.china@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 3 of 19

1. Test Item: Design

Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 6

Test Condition:

Condition: 23 \pm 2 °C, 50 \pm 5 % RH, 24 h

Lab Environmental Condition: 23 \pm 2 °C, 50 \pm 5 % RH

Test Result:

Test Item	Requirement in AS/NZS 2906:2001 Section 6	Conclusion
	(a) All closures shall be designed to allow effective sealing without	
	the use of tools so that the container, other than a tank, will be	Pass
Closures	hermetically sealed in normal use. Threaded closures shall be	The seal at a
and Gaskets	designed to seal at a torque not greater than 5 N·m.	torque is 3.0
	(b) Gaskets, where used, shall be installed with a retaining ring or	N·m.
	other means of preventing accidental loss.	
		Pass
Filling	The filling opening shall be designed to allow free entry of common,	The diameter
Filling	fuel-dispensing nozzles. The opening shall be not less than 25 mm in	of filling
Opening	diameter nor more than 70 mm in diameter.	opening is 35
		mm.





No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 4 of 19

Test Item	Requirement in AS/NZS 2906:2001 Section 6	Conclusion
Pouring Opening	Each container, except tanks for boats, shall be provided with a pouring opening. The pouring opening shall have an integral pouring nozzle, or shall be designed to accept a pouring nozzle. The supply of a detachable pouring nozzle with the container is optional. Means shall be provided for venting during pouring. The junction of the container and adetachable pouring nozzle, if supplied, shall not leak when liquid is poured from the container. To reduce hazards due to electrostatic charging of liquids, the diameter of the pouring nozzle, if supplied with the container, shall comply with the following equation(see AS/NZS 1020): $d \le 640/v^2$ where $d = \text{diameter of pouring nozzle}$, in millimetres $v = \text{flow velocity of liquid}$, in meters per second (0.04 m/s Provided by client)	Pass The diameter of pouring opening is 15 mm
Pouring Vent	A pouring vent shall be incorporated in portable fuel containers (other than tanks) to provide a smooth pouring action without undue pulsation. The pouring vent shall be a second opening or the pouring nozzle shall be vented.	Pass
Breathing Vent	A breathing vent shall be incorporated in demountable fuel tanks for boats to provide a smooth fuel withdrawal without undue pulsation.	Pass



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising it their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approved of the Company. Any unauthorized atteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CAI. Doccheck@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 5 of 19

Test Item	Requirement in AS/NZS 2906:2001 Section 6	Conclusion
Handle	A handle shall be provided. It shall either be an integral part of the container or be secured permanently to the container. The handle shall be located so that it may be used for both carrying and pouring.	Pass
Nominal Capacity Fill Level	A fuel container shall have an embossed or moulded graduation or other suitable means to accurately indicate its fill level when filled to the nominal capacity. The nominal fill level is the recommended fill level.	Pass
Capacity of Container	The container shall have an overflow capacity, to the lowest opening, not less than 105% of the nominal capacity.	Pass Overflow capacity:109 %
Fuel Indicator	It is recommended that fuel tanks for boats be equipped with a suitable fuel level indicating device.	NA
Pouring Nozzle	Where a separate pouring nozzle is supplied, provision shall be made for securing the nozzle to the container or incorporating it in the container.	Pass
Colour	The external surface of the finished container may be of any colour.	The colour is red.



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising it their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approved of the Company. Any unauthorized atteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CAI. Doccheck@sgs.com

No.31 Xianghong Road, XiangAn Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380 www.sgsgroup.com.cn

中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5761588

f (86-592) 5765380 e sgs.china@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 6 of 19

Test Photo:



2. Test Item: Elastomeric Components

Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.2 & Appendix B & ASTM D471-12a

Lab Environmental Condition: 23 \pm 2 $^{\circ}$ C, 50 \pm 5 $^{\circ}$ RH

Test Result:

				Requirement	
Test Item	Test Condition	Test Result		in AS/NZS	Canalusian
rest item	rest Condition	1631	nesuit	2906:2001	Conclusion
				Section 7.2	
			No evidence		
	Immersion condition: ASTM Reference Fuel C, $23\pm2~^{\circ}\mathrm{C}$, 168 h	Comple #1	of cracking		
		Sample #1	or visible	No evidence	
Annogrango			deterioration	of cracking or	Pass
Appearance			No evidence	visible	F 455
		Cample #0	of cracking	deterioration	
		Sample #2	or visible		
			deterioration		



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx, Attention is drawn to the limitation of liability indemnification and jurisdiction issues defined therein. Any holder of this document is advised thin information contained hereon reflect the Company's sindings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exponerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company, any unauthorized attention, foregory of fallsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fulles extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 144 or email: CN_Doccheck@sgs.com



No.: XMIN1502000923PS


Date: Jun 17, 2015

Page: 7 of 19

Test Item	Test Condition	Test	Result	Requirement in AS/NZS 2906:2001 Section 7.2	Conclusion
Change in Volume	Immersion condition: ASTM Reference Fuel C, 23±2 °C, 168 h→ Fresh Fuel C, 23±2 °C, 30 min. Test condition: Deionized water, 23±2°C	Sample #1 Sample #2	18.3 % 8.7 %	A change in volume not greater than 40% swelling or 1% shrinkage	Pass
Mass Loss (Extraction)	Immersion condition: Immerse in ASTM Reference Fuel C, 23±2 °C, 168 h→40 °C, 20 kPa vacuum pressure	Sample #1 Sample #2	3.5 % 2.6 %	A mass loss (extraction) of not greater than 10%	Pass

- Note: 1. Change in Volume, %=(Volume after immersion Volume before immersion)/ Volume before immersion × 100.
 - 2. Mass Loss, %=(Mass before immersion Mass after immersion)/ Mass before immersion×100.
 - 3. ASTM Reference Fuel C: 50 % ISO-Octane and 50 %Toluene by volume.

Test Photo:

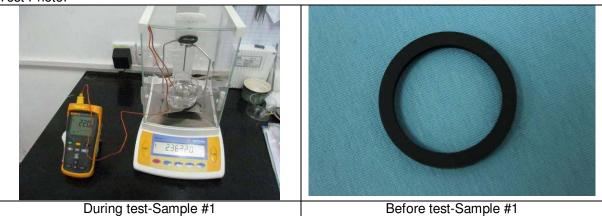



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx.and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-and-Condit

re-remail: CN.Doccheck@sgs.com Na3/Xianfongo Roxi,Xianfah Troin hudistrial Zone,Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380 www.sgsgroup.com.cn 中国-福建•厦门•火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5761588 f (86-592) 5765380 e sgs.china@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 8 of 19







Before test-Sample #2

3. Test Item: Mass Loss Test Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.3.1 & Appendix C

Test Condition:

Condition: Fill with ASTM Reference Fuel B, 23 \pm 2 $^{\circ}$ C, 30 days

Lab Environmental Condition: 23 \pm 2 $^{\circ}$ C, 50 \pm 5 $^{\circ}$ RH

Test Result:

Test Item	Test Result	Requirement in AS/NZS 2906:2001 Section 7.3.1	Conclusion
		The mass Loss shall not	
	Mass Loss :0.3 %	exceed 1 % and all surfaces,	
Mass Loss Test	No tackiness, loss of lining when examined, shall show no		Pass
Wass Loss Test	adhesion and other obvious	evidence of tackiness, loss of	rass
	defects	lining adhesion or other	
		obvious defects	

Note: 1. Mass loss, %=(Mass before filling - Mass after filling)/ Mass before filling×100.

2. ASTM Reference Fuel B: 70 % ISO-Octane and 30 %Toluene by volume.



邮编:361101 t (86-592) 5761588

No.31 Xianghong Road, Xiang'An Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380 www.sgsgroup.com.cn



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 9 of 19

Test Photo:



4. Test Item: Hydrostatic Pressure Test & Stability Test

Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.3.2 & Section 7.3.3 & Appendix L

Test Condition:

Condition: ①After test item 3, empty the sample and stabilize at 23±2 °C for 24 h

pressure, 30 min

③Empty the sample and stabilize at 23±2 ℃ for 24 h

Lab Environmental Condition: 23 \pm 2 °C, 50 \pm 5 % RH

Test Result:

Test Item	Test Result	Requirement in AS/NZS 2906:2001 Section 7.3.2	Conclusion
Hydrostatic Pressure Test	No evidence of leakage	No evidence of leakage	Pass
Stability Test	The specimen remain on its base unsupported	The specimen shall remain on its base unsupported	Pass



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx.and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx, Attention is drawn to the limitation of liability indemnification and jurisdiction issues defined therein. Any holder of this document is advised thin information contained hereon reflect the Company's sindings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exponerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company, Any unauthorized alteration, foregover of alsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fulles extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 144 or email: CN_Doccheck@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 10 of 19

Test Photo:



5. Test Item: Drop Strength Test Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.3.4 & Appendix E

Test Condition:

Condition: ①After test item 3, empty the specimen and stabilize at 23±2 °C for 24 h

②Fill with water, -18 $^{\circ}$ C, 2 h → Take out and do the test immediately

Drop height: 1200 mm

Lab Environmental Condition: 23 \pm 2 $^{\circ}$ C, 50 \pm 5 $^{\circ}$ RH

Test Result:

Test Item	Test Result		Requirement in AS/NZS 2906:2001 Section 7.3.4	Conclusion
	Direction 1	No rupture, no leakage	Specimen shall show no	
	Direction 2	No rupture, no leakage	sign of rupture or leakage	
Drop Strength	Direction 3	No rupture, no leakage	after the specimen has	Pass
Test	Direction 4	No rupture, no leakage	been vented and left to	1 433
	Direction 5	No rupture, no leakage	stand for a period of not	
	Direction 6	No rupture, no leakage	less than 5 min.	



No.31 Xianghong Road, Xiang'An Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380 www.sgsgroup.com.cn

邮编:361101 t (86-592) 5761588 f (86-592) 5765380 e sgs.china@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 11 of 19

Test Photo:



6. Test Item: Integrity Under Exposure to Flame Ttest

Test Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.3.5 & Appendix F Test Condition: Round test tray: 600mm in diameter, 13mm high

> 5L motor spirit in the fuel container 0.75L motor spirit in the round test tray

Test Result:

			Requirement in	
Test Item	Tost Dooult		AS/NZS	Conclusio
rest item		Test Result	2906:2001 Section	n
			7.3.5	
Determination	Sample 1	The sample doesn't lose its integrity		
	Sample	in 30s and doesn't explode in 90s	Sample shall have	
of integrity of	0	The sample doesn't lose its integrity	a time to 'loss of	
fuel	Sample 2	in 30s and doesn't explode in 90s	integrity' of not	
containers		The sample doesn't lose its integrity	less than 30 s and	Pass
when	Sample 3	in 30s and doesn't explode in 90s	shall not explode	
exposed to		The sample doesn't lose its integrity	in less than 90 s.	
flame	Sample 4	in 30s and doesn't explode in 90s		



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx.and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx.attention is drawn to the limitation of liability indemnlification and jurisdiction issues defined therein. Any holder of this document is advised thin formation contained hereon reflect the Company's shortings at the time of its intervention only and within the limits of Cilent's instructions, if any. The Company's sole responsibility is to its Cilent and this document does not exported parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company, Any unauthorized alteration, foregory or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fulles extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

or email: CM.Doccheck@sgs.com | Mo31/Kanghong Read, Xiang/An Torch Industrial 20ne, Xiamen, Fujian Province, China. 361101 t (86.592) 5761588 f (86.592) 5765380 www.sgsgroup.com.cn | 中国・福建・厦门・火炬(羽安)产业区翔虹路31号 邮编:361101 t (86.592) 5761588 f (86.592) 5765380 e sgs.china@sgs.com



No.: XMIN1502000923PS

Date: Jun 17, 2015


Page: 12 of 19

Remark: 1. According to AS/NZS 2906: 2001 7.3.5, when a sample is tested in accordance with Appendix F, it shall have a time to 'loss of integrity' of not less than 30 s and shall not explode in less than 90 s.According to AS/NZS 2906: 2001 4.6, integrity is defined as follow:

The state of being whole or entire. A fuel container is considered to have lost its integrity when it ceases to contain the fuel or its vapour.

Note: Samples are fused in the burning process.

Test Photo:

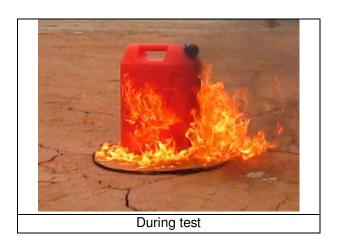

7. Test Item: Handle Strength Test Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.3.6 & Appendix G

Test Condition:

Condition: ①After test item 5, fill with 10 L water, 23 \pm 2 °C, 6 h

Drop height: 305 mm

Lab Environmental Condition: 23 \pm 2 $^{\circ}$ C, 50 \pm 5 $^{\circ}$ RH



No.31 Xianghong Road, Xiang'An Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588

邮编:361101 t (86-592) 5761588

f (86-592) 5765380

f (86-592) 5765380



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 13 of 19

Test Result:

Test Item	Test Result	Requirement in AS/NZS 2906:2001 Section 7.3.6	Conclusion
Handle Strength Test	No separation of the handle, no leakage	There shall be no complete separation of the handle at any point of attachment to the specimen, nor there shall be any leakage from the specimen. When evidence of partial separation of the handle of the specimen is present, the test shall be repeated once more, as specified, on the same handle of that specimen. There shall be no further separation after the repeated test.	Pass

Test Photo:





This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx.and. for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction focuments. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate. please contact us at telephone. (#5,755) 332, 4443.



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 14 of 19

8. Test Item: Resistance to Petroleum Test

Sample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.4.2 & Appendix I & ASTM D638-10

Test Condition:

As received condition: 23 \pm 2 $^{\circ}$ C, 50 \pm 5 $^{\circ}$ RH, 24 h

Condition 1: Fill with ASTM Reference Fuel C, 38 °C, 30 d→ Fresh ASTM Reference Fuel C, 30 min

Condition 2: Fill with the mixture of fuel (see note 2), 38 °C, 30 days→ Fresh mixture of fuel, 30 min

Specimen: Type IV

Testing speed: 50 mm/min

Gauge length: 25 mm

Lab Environmental Condition: 23 \pm 2 °C, 50 \pm 5 % RH

Test Result:

Test Item	Test Result		Requirement in AS/NZS 2906:2001 Section 7.3.2	Conclusion
	As received	25.4 MPa	/	/
Tensile	After filling with ASTM Reference Fuel C	22.3 MPa	/	/
Strength	Retention rate	87.8 %	≥85 %	Pass
ou ongui	After filling with mixture of fuel	24.1 MPa	/	/
	Retention rate	94.9 %	≥85 %	Pass
	As received	710 %	/	/
Florenties	After filling with ASTM Reference Fuel C	790 %	/	/
Elongation at Break	Retention rate	111.3 %	≥85 %	Pass
	After filling with mixture of fuel	770 %	/	/
	Retention rate	108.5 %	≥85 %	Pass

Note: 1. ASTM Reference Fuel C: 50 % ISO-Octane and 50 %Toluene by volume.

- 2. Mixture of fuel: ASTM Reference Fuel A /IRM 903 oil=16: 1(V/V).
- 3. Retention rate, %=Value after filling with Petroleum/Value as received×100.
- 4. All specimens were cut from the sample.



No.31 Xianghong Road, Xiang'An Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380



No.: XMIN1502000923PS


Date: Jun 17, 2015

Page: 15 of 19

Test Photo:




During test

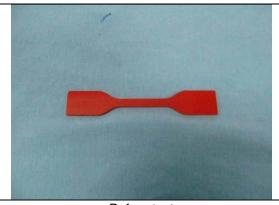






After test - As received

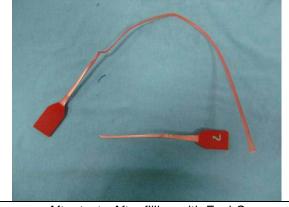

After test -After filling with Fuel C

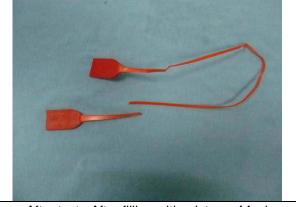

After test -After filling with mixture of fuel



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx.and. for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction focuments. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate.**



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 16 of 19

Test Item: Stress Cracking TestSample Description: See photo

Test Method: AS/NZS 2906:2001 Section 7.4.3 & Appendix J

Test Condition: Fill with 60 $^{\circ}$ C 10% OP-10 solution, with two specimens downward and two specimens

upward in storage, 60 $^{\circ}$ C, 120 h \rightarrow Empty the sample and fill with air and keep the


pressure at 20 kPa

Lab Environmental Condition: 23±2°C, 50±5%RH

Test Result:

			Requirement in	
Test Item	Test Result		AS/NZS 2906:2001	Conclusion
			Section 7.4.3	
Stress	Downward	No leakage, no crack	Shall not crack.	Pass
Cracking Test	Upward	No leakage, no crack	Gridii Hot Gracik.	1 400

Note: OP-10: C₉H₁₉ (C₆H₄)(OCH₂CH₂)_nOH.

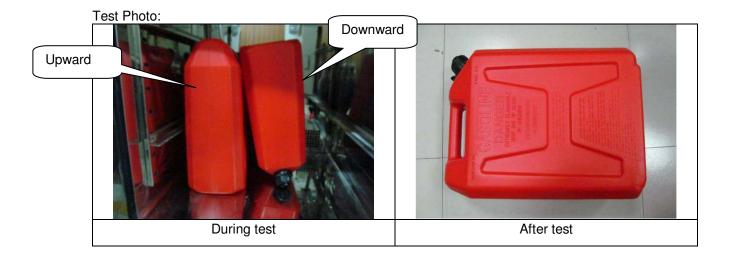



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx, Attention is drawn to the limitation of liability indemnification and jurisdiction issues defined therein. Any holder of this document is advised thin information contained hereon reflect the Company's sindings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exponerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company, any unauthorized attention, foregory of fallsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fulles extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 17 of 19

10. Test Item: Marking

Sample Description: See photo*

Test Method: AS/NZS 2906:2001 Section 8

Test Condition:

Condition: 23 \pm 2 °C, 50 \pm 5 % RH, 24 h

Lab Environmental Condition: 23 ± 2 °C, 50 ± 5 % RH

Test Result:

Requirement in AS/NZS 2906:2001 Section 8	Conclusion	
Each container shall be dumbly and indelibly marked (e.g.		
embossed or moulded) with the following, in characters not less	PASS	
than 3 mm in height for capital letters and for lower case letters	The letters are embossed, the	
with an ascender or descender, or not less than 2 mm in height for	minimum capital letter height	
lower case letters without an ascender or descender:	is 3.42 mm, No lower case	
(a) Manufacturer's name or registered trademark.	letter.	
(b) Nominal capacity. in litres, in conjunction with a mark indicating	(a) "SEAFLO"	
that level	(b) "NOM.CAP.20L"	
(c) An indication of the year of manufacture of the container and,	(c) "Jun, 2015"	
for plastics containers, also the month of manufacture.		



This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.sapx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx, Attention is drawn to the limitation of liability indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects to company's findings at the time of its intervention only and within the limits of Clerk instructions, if any, the Company's sole responsibility in the limits of Clerk instructions, if any, the Company is sole responsibility transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company, Any unauthorize alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fulles extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CM_Doccheck@sgs.com

No.31 Xianghong Road, Xiang'An Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380 www.sgsgroup.com.cn



No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 18 of 19

Each container shall display the following:

- (i) A word indicating the hazardous nature of the contents of the container, i.e. "Warning", "Danger", or "Caution".
- (ii) The warnings, "Vapour may cause flash fire" or similar, "Fuel only" or similar, and "Flammable".
- (iii) Any phrase indicating appropriate cautionary statements, e.g. "Keep out of the reach of children", "Not suitable for racing fuel".
- (iv) First aid information, which shall include advice on actions to be taken if fuel is swallowed, inhaled, or comes in contact with the skin or eyes, e.g. as required by the National Health and Medical Research Council.

PASS

- (i) "DANGER"
- (ii) "FLAMMABLE"
- (iii) "KEEP OUT OF THE REACH OF CHILDREN" (iv) "DANGER HARMFUL OR
- FATAL IF SWALLOWED.IF SWALLOWED, DO NOT VOMITING.CALL

PHYSICIAN IMMEDIATELY"

Note: * means the test samples used are received in the second time.





No.: XMIN1502000923PS

Date: Jun 17, 2015

Page: 19 of 19

Test Photo:





This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/ferms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic to the company state of the co

No.31 Xianghong Road, Xiang'An Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5761588 f (86-592) 5765380 www.sgsgroup.com.cn

邮编:361101 t (86-592) 5761588

f (86-592) 5765380 e sgs.china@sgs.com